

## Synthesis and characterization of certain biodegradable aliphatic polyesters

M. KARUNANIDHI<sup>1</sup>, R. NANTHINI<sup>2</sup> and A. RAVI<sup>3</sup>

<sup>1</sup>Department of Chemistry, Aringar Anna Arts College, Cheyyar, (India).

<sup>2</sup>PG and Research Department of Chemistry, Pachaiyappa's College, Chennai (India).

<sup>3</sup>Department of chemistry, Government Arts College, Thiruvannamalai (India).

(Received: Januray 01, 2010; Accepted: Febraury 01, 2010)

### ABSTRACT

A series of aliphatic copolymers were prepared from, 1,4 butane diol, and suberic acid, succinic / Adipic acid through a two step process of melt polycondensation using titaniumtetraisopropoxide (TTiPO) as catalyst. The synthesized polyesters were characterized by viscosity measurements, nuclear magnetic resonance spectroscopy (NMR), gel permeation chromatography (GPC) X-ray diffraction (XRD) analysis and differential scanning calorimetry (DSC). The polyesters biodegradation was investigated by enzymatic hydrolysis using the enzyme, in a buffer solution with *Candida cylindracea* lipase and *Mucor miehei* lipase. The enzymatic degradation rates for the two different enzymes were observed and compared. The changes in the structure morphology during the degradation process were studied by scanning electron microscopy (SEM). It appears that biodegradation was affected by polyester crystallinity. The lowest crystalline polyester shows highest rate of degradation in both enzymes.

**Key words:** Biodegradable polyesters, aliphatic polymers, Enzymatic degradation.

### INTRODUCTION

Polymeric materials have invaded almost every human activity. This success is primarily due to their low cost, reproducibility at high speed and durability related to a high resistance to physical ageing and biological attacks. The rapid growth of plastics production is considered as a serious source of environmental pollution. Biodegradable polymer is an area that has great promise for being used to integrate life science into the chemical engineering curriculum. A current research area of significant environmental, economic and scientific improvements is biodegradable polymers. In recent years biodegradable polymers have attracted considerable attention as green material and biomaterials in pharmaceutical, medical and

biomedical engineering applications, including drug delivery system, artificial implants and functional materials in tissue engineering.

Great efforts have been and are still being carried out towards the development of novel polymers that are able to undergo controlled biological degradation<sup>1</sup>. Montaudo *et al*<sup>2</sup>. Suggested that there is strong evidence, that microbial biodegradation of synthetic polyesters in nature is also initially caused by hydrolase's secreted from the microorganisms. Studies by Tokiwa and Suzuki<sup>3</sup> reveals that synthetic polyesters can be attacked by hydrolase's. A number of other investigations on the degradation of synthetic polyesters by hydrolases have been published. There are strong evidences that microbial biodegradation of synthetic

polyesters in nature is also initially caused by hydrolases secreted from the microorganisms<sup>4-6</sup>.

Biodegradability of a certain polymer in the form of enzymatic hydrolysis is controlled by several factors. The most important one is the nature of the polymer itself, i.e. its chemical structure, the occurrence of specific bonds along its chain, which might be susceptible to hydrolysis. It is also well known that the degree of crystallinity may be a crucial factor, since enzymes mainly attack the amorphous domains of a polymer. Copolymers with low crystallinity show increased hydrolysis rates. Conditions like temperature, pH and Concentration of enzyme also play a particular role<sup>7-10</sup>. Recent reports have demonstrated that the dominating factor controlling biodegradability of aliphatic polyesters is the mobility of the polymer chains, which is correlated with the difference in the melting temperature of the crystalline action of the polyester and the temperature at which the degradation takes place<sup>11</sup>.

Considering the high commercial potential of aliphatic copolymers and their interesting properties, the present investigation deals with the synthesis and characterization of new type of biodegradable polymer with considerable enzymatic degradability was prepared from suberic acid, succinic /adipic acid and 1,4 butanediol .The structure of their repeating units and the effect of the copolymer composition on the physical and thermal properties as well as enzymatic degradation are investigated. The enzymes *Candida Cylindracea* lipase and *Mucor miehei* lipase were used in the degradation studies.

## MATERIALS AND METHOD

### Materials

Succinic acid (MERCK AR grade), adipic acid, succinic acid and suberic acid (LANCASTER) were recrystallized from deionised water. 1,4 - butanediol (LANCASTER) was dried with CaO overnight and then distilled under reduced pressure. Titanium Tetra isopropoxide (TTiPO) purchased from LANCASTER was used as such. *Candida cylindracea* and *Mucor miehei* lipase were purchased from SIGMA ALDRICH. All the other materials and solvents used for the analytical

methods were of analytical grade.

### Synthesis of Polyesters

Synthesis of polyesters was performed by using three-necked flask containing a mechanical stirrer, condenser and nitrogen inlet tube. The apparatus was charged with 0.1 mol of succinic acid / adipic acid and 0.1 mole suberic acid, 0.2 mole of 1,4-Butanediol. The mixture was heated to 210 °C under nitrogen atmosphere and water was removed as the esterification by product. When water ceased to be generated, predetermined amount of titanium tetra isopropoxide catalyst was placed into the reaction flask. Subsequently, the pressure of the reaction system was gradually decreased and melt polycondensation polymerization was continued at 210°C under a final reduced pressure lower than 0.5mm Hg. The second phase of the reaction was carried out under this condition for 20 hours.

The viscous slurry was cooled in the nitrogen atmosphere. The crude polyester was dissolved in chloroform, precipitated into a 10-fold amount of vigorously stirred ice-cold methanol, and dried under reduced pressure at room temperature. To remove the catalyst residues in the original polyesters, the corresponding original precipitated polyesters were further refluxed at 90°C for a predetermined period using 8 fold molar excess of dilute HCl and then the reaction solutions were similarly precipitated in ice-cold methanol and dried.

The molecular weight and polydispersity index were calculated by Gel Permeation Chromatography (GPC). Physical properties of the synthesized random copolymers were characterized by <sup>1</sup>H NMR, Solution Viscosity measurement, Differential Scanning Calorimetry (DSC) and Wide Angle X-ray Diffraction analysis (WAXD). For all polyesters melting point ( $T_m$ ), glass transition ( $T_g$ ) and enthalpy of fusion ( $DH_m$ ) was recorded. The enzymatic degradation was performed in a buffer solution with *Candida cylindracea* lipase and *Mucor miehei* lipase. The enzymatic degradation rates for the two different enzymes were observed and compared.

### Enzymatic Hydrolysis

Copolyester thin films were obtained by hot pressing method. The thin films of

area  $10 \times 10 \text{ mm}^2$  and about 200mm thickness were placed in a Petri dish containing 10ml of Phosphate buffer solution ( $\text{pH } 7.00 \pm 0.01$ ) with 1mg/mL lipase from *Candida cylindracea*. After a specific period of incubation, the films were removed from the dish, washed with distilled water and weighed till the constant weight was obtained. This procedure was repeated for every chosen time interval: 9,24,48,72 and 90h.

The enzymatic hydrolysis was also carried out with another enzyme *Mucor miehei* using the same procedure as followed for *Candida cylindracea*. The degree of biodegradation was estimated from the weight loss percentage (D)

#### **<sup>1</sup>H NMR studies**

<sup>1</sup>H NMR is a powerful and versatile technique which is useful for the qualitative and quantitative observation of polymer structure. The spectra of the three polymers are given in Fig 2. The <sup>1</sup>H NMR spectra of these polyesters show signals characteristic of terminal and central methylene proton resonance of the tetramethylene group of 1,4-butanediol at 4.04 to 4.1 ppm and 1.69 ppm respectively. The methylene protons of the succinic ester moiety give signals at 2.3 ppm. The terminal and central methylene protons of the sebacic ester residue appear at 1.6 ppm and 1.25 ppm respectively. The terminal and central methylene protons of suberic ester residue appear at about 1.69 ppm and 1.25 ppm respectively.

#### **X-ray Diffraction analysis**

WAXD was used to analyse the crystallinity of the copolymers. Indicative WAXD patterns of the two polyesters are presented in Fig 3. The PBSSu sample exhibited high degree of amorphous nature, due to the lower crystallinity compared to PBASu samples. The comparison of the diffractograms of the polyesters reveals that the crystallinity of polymers increases with the increase in the number of methylene groups in the repeating unit of the polymer chain.

#### **Biodegradation studies**

Hydrolytic cleavage of the polyester chains takes place at random in the polymers. As degradation advances, smaller oligomeric species are formed leading to increase in weight loss and fragmentation of the polymers.

Enzymatic hydrolysis is a heterogeneous process. Enzymes are attached on the surface of an insoluble substrate and hydrolysis takes place via surface erosion. In general, the internal parts of polyester thin films are not attacked until extended holes are created onto surface allowing the enzymes to penetrate and attack the main body .

The enzymatic degradation of the two polyesters PBSSu and PBASu were investigated by *Candida cylindracea* and *Mucor miehei* lipase enzymes. The weight loss of the two copolymers as a function of time is plotted. The enzymatic

**Table 1: GPC measurements of polyesters**

Polymer	[h] <sup>a</sup> dL/g	M <sub>n</sub> g/mol	M <sub>w</sub> g/mol	Poly dispersity index M <sub>w</sub> / M <sub>n</sub>
PBSSu	0.225	5621.8	12627.2	2.25
PBASu	0.335	8548.4	20134.8	2.35

**Table 2: Thermal Data of Suberic acid Polyester Series**

S. No.	Polymer	T <sub>g</sub> (°C)	T <sub>m</sub> (°C)	T <sub>d</sub> (°C)	DH <sub>m</sub> J/g
1.	PBSSu	-43.2	40.0	382.8	93.61
2.	PBASu	-36.2	43.20	375.0	80.6

degradation of co polyesters by *Candida cylindracea* and *Mucor miehei* lipase is exhibited in Fig.4 and 5 respectively

#### Scanning electron microscope analysis

The hydrolytic effect of the two enzymes *Mucor miehei* lipase and *Candida Cylindracea* lipase enzymes on copolymers can be seen in SEM micrographs.

The effect of biodegradation upon the

polymer surfaces was examined using Scanning Electron Microscope, SEM. The morphology of the aliphatic polyesters was observed using SEM after enzymatic degradation. SEM micrographs of thin films taken before and after enzymatic hydrolysis are presented in Fig 6. The SEM micrographs of the polyesters before degradation exhibits a homogenous and smooth surface. The image of polyester films after enzymatic hydrolysis shows small holes and cracks which influence the surface erosion of thin films. The enzymatic degradation was

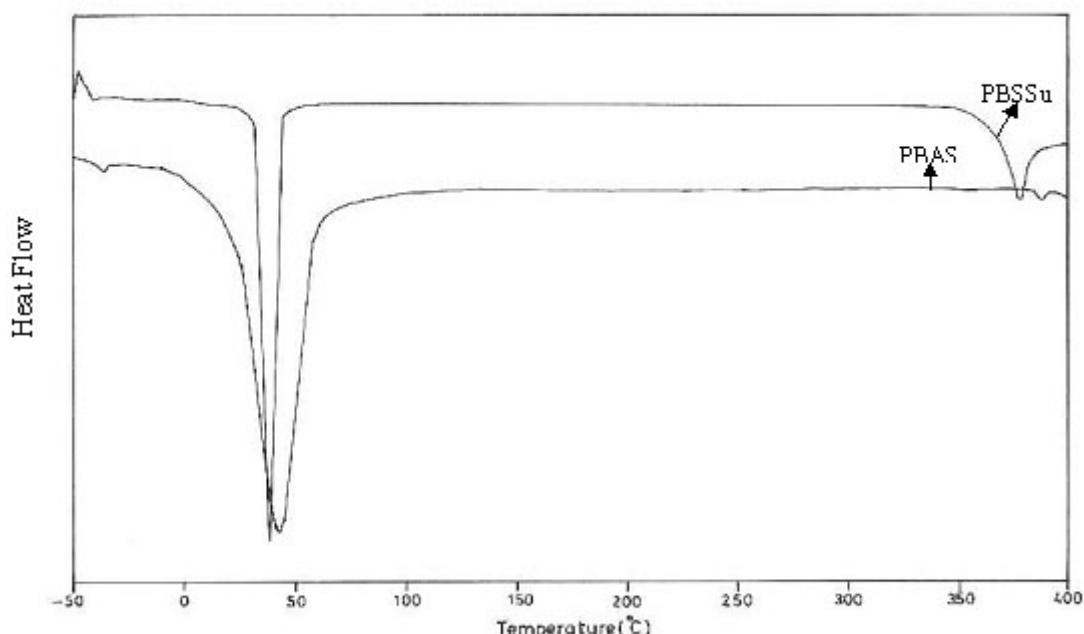


Fig. 1: DSC thermogram of polyesters

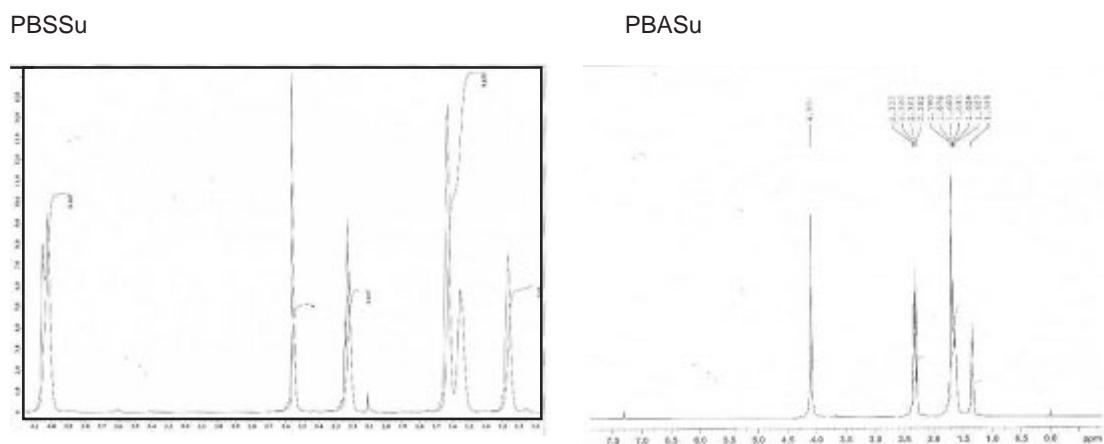


Fig. 2:  $^1\text{H}$  NMR Spectra of copolymers

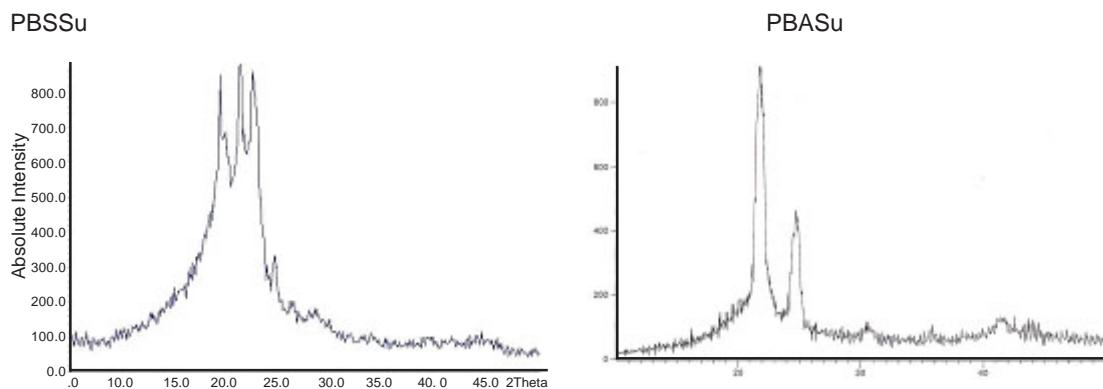
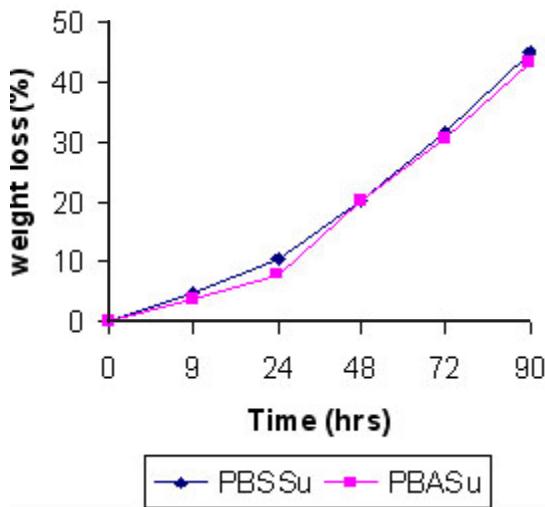
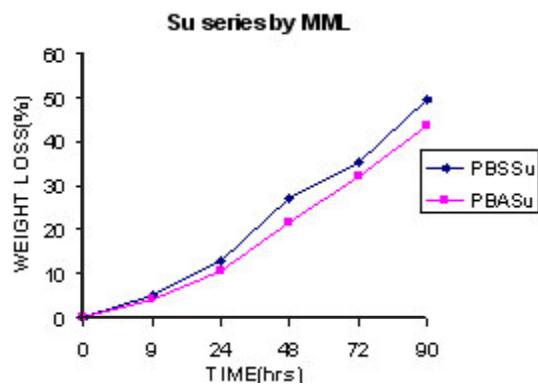


Fig. 3: WAXD diffractogram of polyesters

Fig. 4: Biodegradation analysis of polyesters using *Candida cylindracea* lipase enzymeFig. 5: Biodegradation analysis of polyesters using *Mucor miehei* lipase enzyme

performed using *Candida Cylindracea* and *Mucor miehei*. Though the erosion was observed in both, using *Candida Cylindracea* and *Mucor miehei*, it was slightly higher in the later case than the former. The SEM micrographs of PBSSu demonstrated that hydrolysis occurred all over the surface of polyester thin film creating holes, in contrast to what occurred in PBASu films, where degradation was observed only at specific regions inferring that PBASu have less amorphous regions than PBSSu.

## CONCLUSION

A new type of biodegradable polymer with considerable enzymatic degradability was prepared from suberic acid, succinic /adipic acid and 1,4 butanediol. Enzymatic degradability was determined on the basis of weight loss in buffer solution with lipase enzyme. Disintegration of the copolyesters occurred during degradation. Disintegration of the copolyesters occurred during degradation. The hydrolytic degradation of polyester films in the

presence of *Mucor miehei lipase* is relatively faster than *Candida cylindracea lipase*.

Biodegradation showed that amongst the various parameters affecting polymer degradation, crystallinity was the dominant factor. For this reason, the higher biodegradation rates are observed for the copolymers PBSSu, which exhibit lower crystallinity.

SEM micrographs reveal that hydrolysis occurred at the specific area of the surface of PBSA

and PBSSu specimens, where as the hydrolysis occurred all over the surface of the polyester PBSSu and creating holes. From the thermal analysis data and in comparison with the SEM micrographs, it is established that amorphous areas of polyesters are preferably hydrolysed.

It was concluded that hydrolysis of PBSSu film using both enzymes are higher than that of PBSA as expected due to lower crystallinity and lower melting point of the polymer. Thus, the rate of enzymatic degradation is influenced by the degree of crystallinity of the polymer.

## REFERENCES

1. N. Dimitrios. Bikaris, Z.George Papagorgiou, Dimitris S. Achilias. *J.Polym. Degrad. Stab.*, **91**: 31 (2006).
2. G.Montaudo, P.Rizzarelli, *J.Polym Degrad Stab.*, **70**: 305(2000).
3. Y.Tokiwa. and T. Suzuki., *Nature.*, **270**(3): 76 (1977).
4. J.M. Raquez, P.Degee, R.Narayan, S P.Duboi, *Macromolecules.*, **34**: 8419 (2001)
5. V. Tserki, P. Matzinos, E. Pavlidou, D. Vachliotis,C. Panayiotou,, *J. Polym Degrad Stab.*, **9**: 367 (2006)
6. Y.Ikada, T.H.Suji, *Macromol Rapid commun.*, **21**: 17 ( 2000)
7. D.Bikaris, J.Aburto, I.Alric, E.Born,-don, Betchere et al. *J Appl polym Sci .*, **71**: 1089 (1999)
8. J. Aburto, I.Alric, S.Thiebaud, E.Borendon , D.Bikaris J.Prinos et al., *J Appl Polym Sci.*, **74**: 1440 (1999)
9. G. Seretoudi, D.Bikaris, C.Panijiotot., *Polymer.*, **43**: 5405 (2002)
10. Chia-Jung Tsai, Wei-Che Chang,Chi-He Chen,, Hsin-Ying Lu, and Ming Chen, *Euro. Poly. Journal.*, **44**: 2339 (2008)
11. Jaisankar.V, Nanthini.R, Ravi.A and Karunanidhi. M, *J. Polym. Mater.*, **26**(2): 157 (2009).